

Operating Instructions

Impact Penetration Tester PEP

Code 582-002-189



Use

The Impact Penetration Tester type PEP serves to determine the necessary curing time for safe stripping of molds and cores made from cold, self-hardening sand mixtures and measure the subsurface strength of CO₂-silicate molds and cores. A graduated probe is driven into the mold or core by a series of blows of equal impact. The number of blows required to cause a given penetration of the probe can be related to the subsurface strength of the material being tested, stronger materials requiring more impacts to cause an equivalent depth of penetration. The instrument consists of a hardened steel probe, graduated in one centimetre divisions attached to a hand operated, spring loaded mechanism which subjects the probe to a series of equally strong blows.



For the determination of the safe curing time for molds and cores made of cold-hardening sand mixtures.

*Diameter approx. 22 mm
Length approx. 142 mm
Length with probe approx. 230 mm*

Test procedure

Before screwing the probe into the mechanism, actuate it a few times to ensure freedom of movement. Turn the knurled knob counter-clockwise to the outmost position and press the Impact Penetration Tester against a wooden surface until the blow is released.

The test is carried out as follows:

1. Screw one of the two probes firmly into the instrument.
2. If the mold or core to be tested is expected to be very hard, turn the knurled knob clockwise as far as it will go to give maximum spring pressure on the hammer.
3. Should the mold or core be relatively soft, the knurled knob has to be turned counter-clockwise to give the minimum spring pressure on the hammer.
4. Place the point of the probe on the mold surface. Hold the instrument at right angles to the surface and press the instrument firmly inward until a definite impact is felt. It is important that the spring loaded hammer should be responsible for forcing the probe into the surface and hence only sufficient pressure should be applied by the operator to release the hammer mechanism.
5. Repeat this operation without withdrawing the probe and record the number of impacts necessary to penetrate the mold surface up to the first centimetre mark.
6. Continue impacting the probe into the mold, maintaining it at right angles to the surface, and record the number of impacts necessary for each centimetre of the probe to penetrate the mold.


Note:

To avoid damage to the probe care should be taken to keep the body of the instrument in vertical line with the probe during penetration.

Interpretation of results

It is known that uniform hardening is not normally achieved from the surface to the interior of a mold or core during the hardening process. It is generally desirable to strip a mold from its box as soon as sufficient hardening has developed to avoid distortion or breakage, this time as a rule being much earlier than that of full uniform hardness development.

By plotting the number of impacts per centimetre of probe penetration against the depth of penetration it is possible to assess the hardness or internal strength at varying distances from the mold surface. Routine acceptance tests on cold self-hardening sand mixtures can be carried out with this instrument by assessing the number of impacts required to penetrate the probe a given distance into the mold surface as soon as the required subsurface strength for stripping has been achieved.

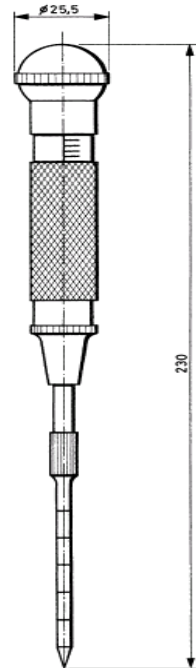

Bibliography:

D. Bird, B.C.I.R.A. Journal, 1967, Vol. 15 pp. 343-349/Report 881

K.E. Nicholas and D. Bird, B.C.I.R.A. Journal, 1968, Vol. 16, pp. 448-454/Report 927

Type:

ID-No.:

Name and address of manufacturer:

Simpson Technologies GmbH
Roizheimer Strasse 180
53879 Euskirchen,
Germany

For other Simpson Technologies offices around the world and for our contact information please visit us on the internet at www.simpsongroup.com on the Contacts page.

This document is strictly confidential.

This document is protected under the copyright laws of the United States and other countries as an unpublished work. This document contains information that is proprietary and confidential to Simpson Technologies Corporation or its subsidiaries which shall not be disclosed outside or duplicated, used or disclosed in whole or in part for any purpose other than to evaluate Simpson Technologies for a proposed transaction. Any use or disclosure in whole or in part of this information without the express written permission of Simpson Technologies Corporation is prohibited.

© 2021 Simpson Technologies Corporation. All rights reserved.